


Industrial scale production of layer materials via intermediate-assisted grinding

November 22 2019

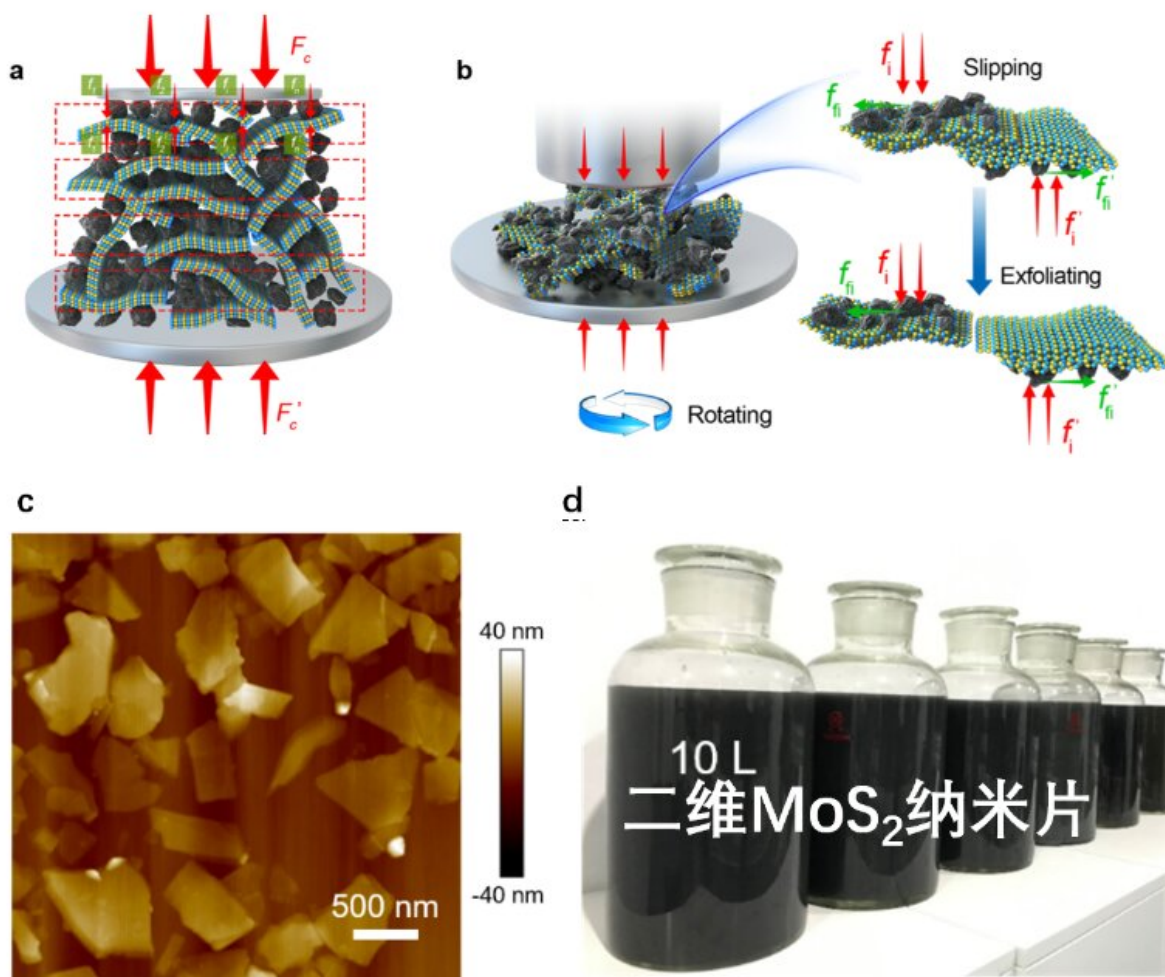

(a) Schematic of the decomposition of the macroscopic compressive forces F_c and F_c' into much smaller microscopic forces f_i and f_i' that were loaded onto the layer materials by force intermediates. (b) Exfoliation mechanism of layer

materials. f_i and $f_i^?$ transfer to sliding frictional forces f_{fi} and $f_{fi}^?$ under the relative slipping of the intermediates and layer materials due to the rotation of the bottom container. (c) Atomic force microscopy image of 2D flakes. (d) Photos of several bottoms of 2D MoS₂ flakes in aqueous solution. Credit: ©Science China Press

A large number of 2-D materials, including graphene, hexagonal boron nitride (h-BN), transition metal dichalcogenides (TMDCs) like MoS₂ and WSe₂, metal oxides (M_xO_y), black phosphorene (b-P), etc, provide a wide range of properties and numerous potential applications, But in order to fully realize their commercial use, the prerequisite is large-scale production.

Bottom-up strategies like [chemical vapor deposition](#) (CVD) and chemical synthesis have been extensively explored but only small quantities of 2-D materials have been produced so far. Another important strategy to obtain 2-D materials is from a top-down path by exfoliating bulk layer materials to monolayer or few layer 2-D materials, such as ball milling, liquid phase exfoliation, etc. It seems that top-down strategies are most likely to be scaled-up; however, they are only suitable for specific materials. So far, only graphene and graphene oxide can be prepared at the tons level, while for other 2-D materials, they still remain in the laboratory state because of the low yield. Therefore, it is necessary to develop a high-efficiency and low-cost preparation method of 2-D materials to progress from the laboratory to our daily life.

The failure of solid lubricants is caused by the slip between layers of bulk materials, and the result of the slip is that the bulk materials will be peeled off into fewer layers. Based on this understanding, in a new research article published in the Beijing-based *National Science Review*, the Low-Dimensional Materials and Devices lab led by Professor Hui-

Ming Cheng and Professor Bilu Liu from Tsinghua University proposed an exfoliation technology which is named as interMediate-Assisted Grinding Exfoliation (iMAGE). The key to this exfoliation technology is to use intermediate materials that increase the coefficient of friction of the mixture and effectively apply sliding frictional forces to the layer material, resulting in a dramatically increased exfoliation efficiency.

Considering the case of 2-D h-BN, the production rate and energy consumption can reach 0.3 g h^{-1} and $3.01 \times 10^6 \text{ J g}^{-1}$, respectively, both of which are one to two orders of magnitude better than previous results. The resulting exfoliated 2-D h-BN flakes have an average thickness of 4 nm and an average lateral size of $1.2 \text{ }\mu\text{m}$. Besides, this iMAGE method has been extended to exfoliate a series of layer materials with different properties, including graphite, Bi_2Te_3 , b-P, MoS_2 , TiO_x , h-BN, and mica, covering 2-D metals, semiconductors with different bandgaps, and insulators.

It is worth mentioning that, with the cooperation with the Luoyang Shenyu Molybdenum Co. Ltd., molybdenite concentrate, a naturally existing cheap and earth abundant mineral, was used as a demo for the industrial scale exfoliation production of 2-D MoS_2 flakes.

"This is the very first time that 2-D materials other than graphene have been produced with a yield of more than 50% and a production rate of over 0.1 g h^{-1} . And an annual production capability of 2-D h-BN is expected to be exceeding 10 tons by our iMAGE technology." Prof. Bilu Liu, one of the leading authors of this study, said, "Our iMAGE technology overcomes a main challenge in 2-D materials, i.e., their mass production, and is expected to accelerate their commercialization in a wide range of applications in electronics, energy, and others."

More information: Chi Zhang et al, Mass Production of Two-Dimensional Materials by Intermediate-Assisted Grinding Exfoliation,

National Science Review (2019). [DOI: 10.1093/nsr/nwz156](https://doi.org/10.1093/nsr/nwz156)

Provided by Science China Press

Citation: Industrial scale production of layer materials via intermediate-assisted grinding (2019, November 22) retrieved 6 May 2024 from <https://phys.org/news/2019-11-industrial-scale-production-layer-materials.html>

This document is subject to copyright. Apart from any fair dealing for the purpose of private study or research, no part may be reproduced without the written permission. The content is provided for information purposes only.